

Corrosion of Steel Rebar in Concrete: A Review

Akib Javed, Md Mahamud Hasan Tusher[†], Md. Shahidul Islam Shuvo, and Alisan Imam

*Department of Materials Science and Engineering, Rajshahi University of Engineering and Technology (RUET),
Rajshahi-6204, Bangladesh*

(Received February 27, 2023; Revised April 22, 2023; Accepted April 22, 2023)

Rebar is embedded in concrete to create reinforced concrete (RC). Rebar carries most of the tensile stress and gives compressively loaded concrete fracture resistance. However, embedded steel corrosion is a significant cause of concern for RC composite structures worldwide. It is one of the biggest threats to concrete structures' longevity. Due to environmental factors, concrete decays and reinforced concrete buildings fail. The type and surface arrangement of the rebar, the cement used in the mortar, the dosing frequency of the concrete, its penetrability, gaps and cracks, humidity, and, most importantly, pollutants and aggressive species all affect rebar corrosion. Either carbonation or chlorides typically cause steel corrosion in concrete. Carbonation occurs when carbon dioxide in the atmosphere combines with calcium within the concrete. This indicates that the pH of the medium is falling, and the steel rebar is corroding. When chlorides pass through concrete to steel, corrosion rates skyrocket. Consideration must be given to concrete moisture. Owing to its excellent resistance, dry concrete has a low steel corrosion rate, whereas extremely wet concrete has a low rate owing to delayed O₂ transfer to steel surfaces. This paper examines rebar corrosion causes and mechanisms and describes corrosion evaluation and mitigation methods.

Keywords: Reinforced concrete (RC), Steel Rebar, Carbonation Corrosion, Chloride Corrosion, Corrosion Monitoring

1. Introduction

One of the biggest threats to the long life of concrete buildings is steel corrosion. Due to environmental factors, concrete structures deteriorate, and RC buildings fail to meet expectations. The estimated design service life is an important consideration for engineers and researchers—the corrosion rate of the structure. The corrosion depends mainly on maintenance and exposure conditions. Chemical or electro-condition sections are mainly responsible for occurring deterioration of concrete structures. This chemical or electrochemical action is mainly governed by carbonation, specifically of the concrete structure and chloride ingress. Two basic reasons cause rebar corrosion in concrete buildings. Ingress of chloride ions and carbonation are major contributors. When chloride ions are introduced into concrete in excess of the threshold value, corrosion occurs in concrete structures. Again, corrosion will occur in concrete structures if carbonation depth exceeds the concrete cover. If corrosion occurs in

concrete structures, it will reduce the service life of that structure. Corrosion occurs, and the service life of a concrete building is shortened if there is sufficient moisture and oxygen present at the rebar level [1].

The major cause of failure in concrete construction is the corrosion of steel rebar. Around two tons of concrete are used annually for every person on Earth. It has been shown that cement use may be reduced by constructing long-lasting buildings. Steel corrodes in damp environments because airborne contaminants seep through the concrete cover. Damage to concrete from corrosion may increase its volume by a factor of six to ten compared to that of steel. An example of a structure's failure.

Corrosion agents like carbon dioxide or chloride ions increase at the places of crack and create corrosion [2]. If we use low permeable concrete, it will prevent corrosion from the concrete structure. The corrosion inhibitor will be able to penetrate the surface less deeply. Conversely, concrete with a high resistivity will slow the pace of corrosion by impeding the transfer of electrons from the anode to the cathode [3].

[†]Corresponding author: tusher1998bd@gmail.com

In most instances, the mass lost due to corrosion in concrete buildings is inconsequential. But fatigue life and mechanical strength significantly reduce the corrosion region of the rebar. Normally crack growth rates are large, and the pitting rate is relatively low in the corroded region. So it is important to find out the problems at the early stage of the corrosion. That's why a large electrochemical or non-electrochemical, or sensor-based process is used to diagnose rebar corrosion.

This research aimed to study the premature deterioration of RC composite structures due to embedded steel corrosion on reinforced concrete buildings, which has become a severe concern worldwide. Identification of the root causes and the major factors which are primarily responsible for rebar corrosion was a preliminary task of this project. First of all, it was intended to check the effects of humidity and environmental issues on the reinforced concrete composite structure. Then to study the chemical processes that take place in rebar corrosion. Studying the methods that need to conduct the corrosion evaluation was also a part of our project. Finally, our last objective was to discuss a few Methods that could be used to protect the structures from corrosion.

2. The corrosion mechanism



According to the nomenclature established by the American Society for Testing and Materials (ASTM), a material's characteristics will deteriorate, and its corrosion rate will increase if the substance has a chemical or electrochemical interaction with its surroundings [4]. As corrosion is detrimental to the structure, it's important to comprehend how and why it occurs. A decaying process follows the extraction of metals from the ore as the ore interacts with its surroundings. Except for platinum and gold, every metal is thermodynamically unstable in a typical atmosphere. When exposed to heat, it generally converts to a more stable form, such as iron oxide or rust. Three basic elements are important to occur corrosion.

Firstly, At least two metals at different energy levels will be present on a single metal.

Secondly, corrosion can only occur in the presence of an electrolyte.

Thirdly, metallic connections are also required to create corrosion in concrete.

Without these three basic elements, corrosion won't occur. There will occur anodic and cathodic reactions in an electrochemical process. The "corroding" metal is responsible for the anodic reaction, whereas the "corrosive" chemical species are responsible for the reduction process (cathodic reaction). When two half-reactions are combined, corrosion will occur. Both half reactions should maintain the reaction rate to ensure equal production and should maintain the charge balance. Without an external source, it proceeds the electrochemical reaction [5].



When metals corrode, this is the most typical cathodic response. The cathodic reaction of metal is mostly dependent on the oxygen and pH levels present [5].

3. Reinforced concrete buildings' rebar corrosion

Chlorides are the main corrosive agents. It can ingress concrete from different sources. By using contaminated aggregates or groundwater, seawater can be cast into the concrete. Diffusion into the cement might occur. Sea salt spray, de-icing salts, and direct wetness from the ocean all contribute to this dispersed effect. The diffusion of chlorides into concrete lowers the alkalinity of the pore solution. Eventually, rusting will set in. The alkalinity of the pore solution has a significant impact on the longevity of steel embedded in concrete. Alkaline steel (pH > 13) becomes passive when exposed to air or oxygen. It will form a surface layer of Fe_2O_3 .



If the RC structure is subjected to deicing salts, the Fe_2O_3 layer will deteriorate. It will also be reduced if the RC construction is submerged in seawater or if the water used in the concrete mix has a high chloride concentration. Chloride penetration into cured concrete and subsequent corrosion of reinforcement bars is slowed. In such cases, passivation will protect the rebar. However, the alkalinity of the cement will prevent the passivation process from working, leaving the steel vulnerable to corrosion and rust. The cathodic reaction requires the presence of

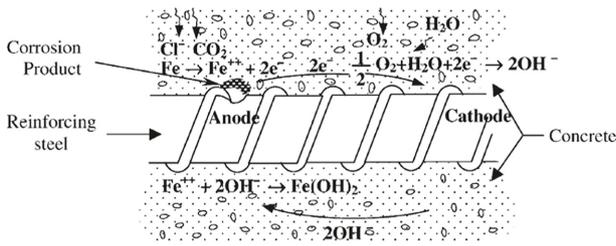


Fig. 1. Anodic and cathodic reactions in steel corrosion [7]




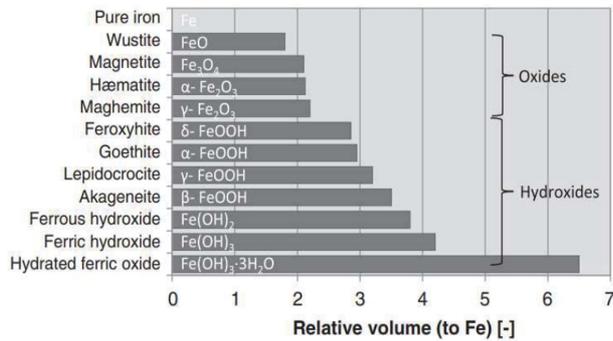


Fig. 2. Relative volumes of iron and its oxides and hydroxides [8]

oxygen and water. The following diagram illustrates the cathodic and anodic reactions in Fig 1. The process of rust formation, this is the initial stage. There will be a chain reaction where ferrous hydroxide turns into ferric hydroxide, which then turns into hydrated ferric oxide, often known as rust [6]. The basic reactions of corrosion are given below:



The volume of hydrated ferric oxide is higher than that of steel. It will become more expansive and porous if it becomes hydrated. The volume at the contact of the concrete will grow by six to ten times, as shown in Fig. 2. This will lead to spalling and cracking in the structure.

4. Corrosion in Concrete


There are primarily two forms of corrosion that may be caused in concrete. These are:

1. Carbonation-related concrete corrosion
2. Corrosion of concrete caused by chloride

4.1 Carbonation-induced corrosion

Indeed, from 1950 to 1980, steel corrosion in carbonated concrete was a serious concern in study and practice. The research findings result in the demand for dense concrete (lower w/c ratio), concrete property control, and a significant increase in cover depth (from 20 mm to 35 mm) in the codes of practice. The European concrete standard EN 206-1, published in 2000, classified the risk of carbonation-induced corrosion based on the severity of the environment. (XC1 to XC4). With the recommendations' minimum requirements (maximum w/c ratio, minimum cement content, minimum cover depth), codes of practice have since given instructions for reinforced concrete rendered with Portland cement to prevent carbonation-induced corrosion for structures with anticipated service lives of 50 or 100 years.

When carbon dioxide gases and alkaline hydroxides interact with each other in concrete, carbonation will occur. Carbonic acid will form when carbon dioxide (CO_2) gases dissolve in water. Carbonic acid neutralises the alkalis in pore water, but it doesn't destroy cement paste, and it will form calcium carbonate. This calcium carbonate fills that pore [6], [9].



It's important to note that the carbonation process involves calcium hydroxides and the unhydrated cement component [10]. Carbon dioxide (CO_2), calcium hydroxide ($\text{Ca}(\text{OH})_2$), and water are the three main ingredients in making calcium carbonate. Permeable pores contain water, and atmospheric carbon dioxide may be detected. Most of the calcium in concrete will either dissolve or stay as calcium silicate hydrate (CSH) or calcium hydroxide. A figure (Fig. 3) is given to understand the process:


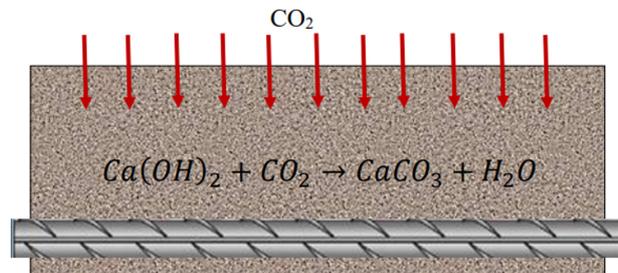


Fig. 3. Schematic diagram of CO_2 ingress [11]

At first, carbonic acid (H_2CO_3) will form in the pore.



Then carbonic acid will react with the calcium phase.



After that, $Ca(OH)_2$ changes to hydrate CSH and free CaO , which helps carbonation.



Because of this reaction pH value will decrease from 12.6 to 8.0. In that situation, the passive layer can't protect steel from corrosion [6].

4.2 Chloride-induced corrosion

If there are chloride ions present in the concrete structures, rebar corrosion will occur. Because of their passive film, it will induce localised disintegration. It begins to solidify mostly at first around the steel. Because of their formation alkaline nature of the pore solution is seen in the concrete [12,13]. The main corrosive agent's chlorides are ingress in the concrete from different sources. There are two possible origins for these chloride ions: the environment, in the case of a hardened substance, or tainted mixing components, in the case of a fresh substance [14-16]. When corrosion is caused by chlorides diffusing through concrete, the alkalinity of the pore solution decreases. pH level will be between 13 to below 7. There's a minimum requirement before you can go forward. In other words, a threshold level of chloride concentration at the rebar is reached when the concentration reaches a certain value [17-20]. Chloride ions lower the interfacial surface tension. Because of this, it will be weak the passive film and form cracks and flaws in the concrete [21]. Montemor and his co-researchers [22] proposed that when the adsorption of Cl^- with a regular displacement of O^{2-} from the passive layer, then the passive layer destruction will take place. There are two main stages in the life cycle of chloride ions: the onset and the spread [22].

5. Methods to evaluate corrosion

Corrosion is mainly a chemical process. It isn't that much easy process to determine its magnitude and damage system. With the help of modern science, nowadays, there

are some methods to evaluate corrosion. These methods are given below:

- Half-cell potential method
- Coulostatic techniques
- Galvanostatic pulse method
- Ultrasonic Guided Waves
- X-ray diffraction and atomic absorption
- Linear polarisation resistance (LPR)
- Time domain reflectometry (TDR)

5.1 Linear Polarization resistance (LPR)

To measure rebar corrosion rates, it is an effective electrochemical process. Corrosion rates of rebar are determined by examining the correlation between the electrochemical process and the current produced between electrically charged electrodes. By using this technique, it will polarize the rebar with an electric current. Afterward, it will observe the potential difference between the reference electrode and the electrodes. A low-voltage DC power source and a reference electrode are often used for this purpose. In the first step, the potential difference between the reference electrode and the working electrode is determined. The reinforcement is then subjected to a bit of current that is transferred from the reference electrode. Corrosion current is related to shifts in the voltage between the reference electrodes, as shown in Fig. 4 [23].

$$I_{corr} = \frac{B}{R_p}$$

Here, B = constant (in volts)

R_p = polarisation resistance (in Ohms)

In concrete, B = 26 mV to 52 mV [24]

$$R_p = \frac{\text{Change in potential}}{\text{Applied Current}}$$

A schematic diagram of an LPR test is given in Fig. 4:

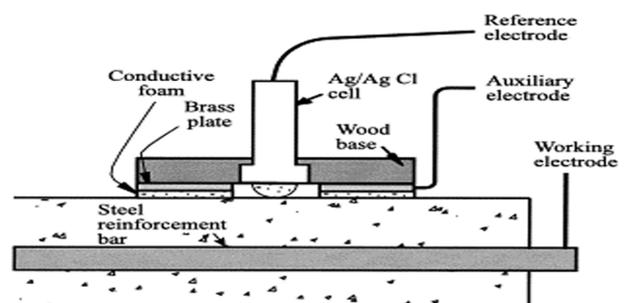


Fig. 4. LPR measurement set-up [25]

The surface of the concrete is perturbed by the use of an extra electrode. Steel's polarized surface area is tucked away behind the auxiliary electrode. When it leaves the electrode, the current can go anywhere it pleases. It will eventually affect a much bigger region of steel [26]. This will give inaccurate information about the surface area of polarised steel. It will create a problem in corrosion density calculation. To fix this issue, engineers created an additional auxiliary guard ring electrode to shield the inner auxiliary electrodes [27-31]. This method is useful for keeping the LPR system confined and decreasing perturbation current from the main inner auxiliary electrode. To choose the proper confinement current, two sensor electrodes are positioned between the outer and inner auxiliary electrodes. Potential difference is monitored in these sensor electrodes, and to maintain potential difference throughout the system, confinement current is selected [32]. In most cases, this method creates a new issue when used on concrete. The most significant drawback of this method is the presence of irregular disturbances in the electrical output. To solve this problem, a model is designed, which is called a dimension line. By using this model, it will overcome its problem [33,34]. This model clearly differentiated between the behavior of active states of steel and passive states of steel. Nowadays, by using this process, corrosion rates of rebar are estimated [35].

5.2 Gravimetric Measurement Techniques

The corrosion rate may be estimated quite well by measuring mass loss. The experimentation is so simple and easy to replicate. To do this experiment, time is needed, and this is so destructive method. The procedure is so simple as to reduce propensity. It will introduce systematic errors. Mass can be measured so easily, about 0.1 mg. Mass loss measurement sensitivity is also limited. It is carried out for an extended period of time to get a rating average across a broad area and over a period of time.

5.3 Alternating current impedance spectroscopy techniques

The term "electrochemical impedance spectroscopy" is also often used to describe this technique (EIS). The RC specimen is subjected to a train of low-amplitude

alternating current (AC) potentials at varying frequencies. The answers will be measured, and a frequency-domain analysis will be performed. This is hugely used in the laboratory field because of its sophisticated measurement system. It is time-consuming and difficult to interpret. It is currently often used to learn about the kinetics of rebar corrosion, as well as to get insight into the mechanism of the steel-concrete interface [36].

5.4 Sensor-based corrosion monitoring

Recent developments in utilising intelligent and sophisticated materials and procedures have opened up new options for NDE (Non-Destructive Evaluation) and SHM. The enhanced responsiveness, higher resolution, and unlimited damage diagnosis capability of smart materials like fibre optics and PZT have substantially assisted online monitoring. Corrosion volume in RC structures has been researched in recent years using these measuring parameters, and concerns concerning corrosion of rebar or piezo ceramics or sensors based on optical fibres have also been investigated [37]. A fibre optic corrosion sensor was developed by Gao et al. in 2011. A fibre bragg grating (FBG) sensor, double steel rebar elements, and protections were included in the design of this sensor. Using the gravimetric loss approach and the fluctuation in the reflected wavelength induced by the gating, the weight loss rate of the rebar was estimated. This was brought about via a series of accelerated corrosion tests. Applying this hypothesis, researchers determined that the bigger the shift in wavelength, the quicker the rebar lost weight. Park et al. (2007) [38] committed PZT sensors to the use of impedance-proving chips and a self-sensing macro fibre composite (MFC) patch. This method assisted in quantifying and detecting corrosion in aluminum buildings [38]. Yang et al. (2013) [39] did an experiment, and by using the EMI technique, the local corrosion of steel beams was monitored. After doing this, he found a quantitative relationship. This relationship exists between corrosion time and the damage index. This provides a reference point for future local corrosion monitoring [39].

5.5 Half-cell potential method

Corrosion evaluation and detection are crucial. Corrosion in concrete cannot be detected without regular inspection.

If a concrete building is damaged, it may be repaired in the best way that is possible. The corrosion state of reinforcing bars may be ascertained using this method [40]. If a break in the concrete is fixed without first treating the rusted steel, the corrosion will likely spread, and the repair will fail. Several different techniques exist for testing and assessing corrosion in reinforcing steel. However, many researchers agree that the half-cell potential is the most important tool. An external electrode connected to a voltmeter measures the potential difference between the steel reinforcement and the outside environment. A metallic rod represents the cell's half. This metal rod is immersed in a solution of its own (Cu/CuSO₄ or Ag/AgCl). A voltmeter is used to join the metal rod to the reinforcing metal. In order to have a good electrical connection, you need to prep the surface and damp it down. The primary use of this approach occurs in the natural environment. A wet concrete cover connects an external electrode to steel reinforcement. Fig. 5 is shown

below:

In order to accurately calculate the half-cell potential of reinforced concrete buildings, a high level of expertise is necessary. Corrosion rate and kind may be determined using this setup [42]. The potential half-cell test may be affected by a number of variables, including the thickness of the covering, the resistivity of the concrete, and the presence or absence of oxygen. This apparatus measures the potential disparity between the two surfaces. Each location on the surface may be used to determine the

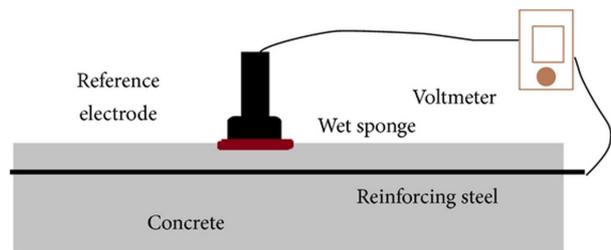


Fig. 5. Set-up of half-cell potential measurement [41]

Table 1. Corrosion criteria for steel in the concrete according to ASTM C876-91, including a variety of standard half-cells [43-45]

Serial no	Half potential cell (mV) Cu/CuSO ₄	Half potential cell (mV) Ag/AgCl	Half potential cell (mV) Hydrogen Electrode	Half potential cell (mV) Calomel	Probability of corrosion
1	>-200	>-106	> +116	>-126	10%
2	-200 to -350	-106 to -256	+116 to -34	-126 to -276	intermediate
3	< -350	<-256	<-184	< -184	90%

Table 2. Corrosion evaluation techniques for concrete buildings

Method	Principle	Advantages	Limitations
Galvanostatic pulse method	Based on the polarisation of rebar by means of a small constant current	Measures half-cell potential and electrical resistance simultaneously	Unstabilised readings
Linear polarization resistance (LPR)	The electrical conductivity of fluid can be related to its corrosiveness	Rapid and requires only localised damage, more detailed information	Measurements are affected by temperature and humidity
Half-cell potential	The electric potential of rebars is measured relative to half-cell and indicates the probability of corrosion	Simple, portable, results in the form of equipotential contours	Needs preparation, saturation required, not very accurate, and time-consuming
Time domain reflectometry (TDR)	To make a transmission line, attach a sensor wire along with the reinforcement. The electromagnetic characteristics of the line will be altered if the reinforcement has physical flaws.	Stronger, less complicated, finds corroded areas and measures the amount of the damage.	Less sensitive
Ultrasonic guided waves	Based on the propagation of ultrasonic waves	Identify the location and magnitude of corrosion	Not very reliable
X-ray diffraction and atomic absorption	The intensity of X-ray beams reduces while passing through a material	Simple and reliable	Hazardous

potential. Once again, this technique allows potential to be measured at several points to assess the risk of corrosion. A greater degree of negativity indicates a greater likelihood of rusting. Below is a table. 01 for half cells that follow ASTM C876-91.

This potential is also called the half-cell potential when the circuit is open. Using the values for the potential at half-cell distances is one way to draw a potential contour. Its goal is to figure out how likely it is that corrosion will happen in different places on the outside of concrete buildings. High negative potentials can be used to find and fix parts of a building that are likely to rust.

Many techniques, together with their underlying assumptions, are outlined in Table 2 for assessing corrosion in concrete buildings:

6. Methods to Protect Structures from Corrosion

In order to prolong the useful life of RC buildings, it is necessary to entirely shield reinforcing steel from corrosion. Methods of chemical and mechanical corrosion protection for concrete buildings are developed. Coatings, protection systems, and other measures have been utilized to lessen the effects of corrosion and the penetration of hazardous ions like moisture and oxygen into the concrete. Several types of corrosion inhibitors and shielding systems are mentioned below:

Adding fly ash to concrete made it more resistant to corrosion. The penetration rate of harmful ions will decrease if the porosity of concrete is reduced [46]. Mineral admixtures & and super-plasticizers such as granulated blast furnace slag, fly ash, and pozzolanic materials decrease the corrosion rate [47]. Low-nickel stainless steel rebars reduce corrosion rate. So, by providing a high alkaline concrete pore solution it will reduce corrosion [48]. Anti-corrosion protection is increased when amino alcohol is used [49]. Carbonation depth will reduce by using a calcium nitride-based corrosion inhibitor [50]. The chloride threshold value will increase by using calcium nitrite. Corrosion inhibitor benzotriazole improves corrosion resistance [51]. If poly-vinyl-pyrro-lidone is added to concrete, corrosion resistance will proven [52]. Alkylamino alcohol will also increase corrosion resistance [53]. Using fusion bonded epoxy coated (FBEC) steel bars helps reduce corrosion

[54]. Steel bars with a DINITROL AV 30 coating have increased resistance to rust and corrosion [55]. ZnO decreases the chloride content & concrete porosity and at the rebar level. It reduces the corrosion in RC structures [56]. The corrosion rate can be reduced by providing high chromium steel [57]. Corrosion-induced growth may be mitigated with the use of CFRP laminates. It slows down the pace at which mass is being lost to corrosion [58]. Protecting concrete against extreme corrosive conditions is possible using ground granulated blast furnace slag (GGBFS), fly ash/GGBFS, silica fume, the double combination of calcium nitrite, and triple combination of calcium nitrite [59]. When used as a repair product or admixture, amino alcohol emerges mixed (inorganic/organic) inhibitors to reduce corrosion [60].

7. Latest Attempts at Monitoring Corrosion

There are a variety of methods used nowadays to assess and track the corrosion of rebars in concrete buildings. It will aid in determining the extent of the corrosion and its root cause. The following are brief summaries of a few investigations conducted by different groups of scientists and researchers:

7.1 Case 01

1. Study performed: Provide a resource for clarifying half-cell potential measurement results. It explains how the corrosion risk, coating thickness, temperature, concrete resistivity, and anode-to-cathode ratio all affect the half-cell potential value. A structure is established by using Laplace's equation. It establishes a relationship between corrosion current and average surface potential, temperature, resistivity, concrete cover, and potential difference in concrete [42].

2. Significant observations: Low resistance potential dispersion in concrete will reveal potential at the steel-concrete surface. It is possible to get better outcomes by providing a potential-based rationale for resistivity data. The gap between interface and surface potentials grows as concrete coating rises.

3. Comments: More reliable results may be expected after calculating the oxygen content and conducting tests at many locations. Increasing confidence requires more experimental validation of the technique.

7.2 Case 02

1. Study performed: Corrosion in concrete structures may be measured using a variety of non-destructive, and electrochemical techniques, which are discussed below [25].

2. Significant observations: By combining several methods, it is possible to get a clearer knowledge of the corrosion condition of steel bars. Existing and new concrete buildings may benefit from a tighter regulating system, which may save inspection expenses.

3. Comments: Using the presented technologies would be helpful in keeping an eye on corrosion in concrete structures. All of these reevaluated methods have promise for enhancing corrosion monitoring in both precision and quality.

7.3 Case 03

1. Study performed: In order to predict the remaining service life of structures, a summary of corrosion monitoring systems and corrosion processes is provided. Capillary water, oxygen availability, electrolyte pH, and Fe^{2+} concentration in concrete near reinforcement all affect the rate of corrosion [3].

2. Significant observations: The half-cell potential, the corrosion current density, and the concrete's resistivity were used to determine the level of corrosion.

3. Comments: Detailed information on corrosion was provided, which might be useful for understanding the concept, identifying causal elements, estimating the lifespan of corroded structures, and monitoring its development.

7.4 Case 04

1. Study performed: Explained how to evaluate corrosion using a variety of techniques, including the linear polarisation method, electrochemical impedance spectroscopy, galvanostatic pulse technique, macro-cell current measurement, half-cell potential, and scanning reference electrode technique [2].

2. Significant observations: Corrosion may be easily measured throughout a whole structure using nondestructive technologies, which are also beneficial due to their low cost and rapid turnaround time for findings.

3. Comments: Provided a high-level overview of several non-destructive technologies, including their

benefits and drawbacks as determined by inference and experience. This research is quite useful since it examines almost all of the prevalent approaches used today to detect corrosion.

7.5 Case 05

1. Study performed: A summary of the corrosion process and nondestructive assessment techniques, such as the concrete resistivity test, linear polarisation method, and half-cell potential method was submitted [40].

2. Significant observations: Several elements, such as moisture content, temperature, and oxygen availability, affect the rate of corrosion in a concrete structure. To get satisfactory findings, corrosion determination must be repeated at regular intervals.

3. Comments: The behavior of electrolytic cells has been stirred to constitute a useful overview.

7.6 Case 06

1. Study performed: Corrosion in reinforced concrete buildings will be assessed using a galvanostatic pulse transient system, with its benefits over a linear polarization (LPR) system also being shown [61].

2. Significant observations: The galvanostatic pulse transient technique typically yields greater corrosion rates than the linear polarisation approach.

3. Comments: Improving maintenance and safety requires research into methods for properly estimating the rate of corrosion in RC structures.

7.7 Case 07

1. Study performed: To evaluate the impact of coatings on the accuracy of these reports, nondestructive electrochemical studies of corrosion are used [62].

2. Significant observations: It was deduced from the findings that coatings had little to no effect on half-cell potential readings.

3. Comments: This research will be useful in determining the accuracy of corrosion monitoring techniques.

7.8 Case 08

1. Study performed: The relative humidity of submerged RC structures was measured and compared to other environmental factors to determine the half-cell corrosion potential [63].

2. Significant observations: This study's experimental results demonstrate that the half-cell potential does not correctly represent the real corrosion rate of underwater RC structures and that prices must be changed correspondingly.

3. Comments: This research qualifies scientists to assess the state of buried RC structures using underwater corrosion measurements.

7.9 Case 09

1. Study performed: After 50 years, the use of half-cell potential measurements was studied to assess the likelihood of corrosion and repair. This is interpreted on a concrete building that has deteriorated [64].

2. Significant observations: It is believed that half-cell potential measurements may be used to assess the corrosion risk.

3. Comments: Research was conducted on the application of the half-cell potential system.

7.10 Case 10

1. Study performed: Using ground penetrating radar, a novel technique to analyse the corrosion of steel bars in concrete was developed (GPR). The potential difference between two moving probes with no connection to steel bars will be measured [65].

2. Significant observations: It demonstrated that ground penetrating radar could detect the electrochemical corrosion process.

3. Comments: Further research and experimentation are required to establish a correlation between laboratory outcomes and real temporal structures.

7.11 Case 11

1. Study performed: Investigate the impact of cover depth and conductivity on the distribution of macro-cell current. On locally corroded reinforcing bars, polarisation measurement methods are seen [66].

2. Significant observations: Investigate the effect of different cover densities and conductivities on the flow of current in macro-cells. Methods for evaluating polarisation are used to examine rebars with localised corrosion.

3. Comments: The impact of macro-cell corrosion on corrosion monitoring was investigated.

7.12 Case 12

1. Study performed: The results of research comparing the effectiveness of two corrosion measurement systems—the conventional and the high performance—in identifying the corrosion activity of steel bars linked in two distinct kinds of concrete specimens were discussed [67].

2. Significant observations: According to the findings, only 24% of specimens would have the same corrosion assessment using all three systems.

3. Comments: Comparing several corrosion monitoring methods for the purpose of improvement. This experiment may help scientists identify a more effective corrosion monitoring method.

7.13 Case 13

1. Study performed: Evaluation of chloride-induced corrosion using electrochemical tools: a discussion of challenges. Factors impacting the results of electrochemical operations are identified, and laboratory testing and electrochemical methods are used to cast concrete so that more tests may be performed in less time and at a lower cost [68].

2. Significant observations: The condition of the rebars was not accurately reflected by the results of the electrochemical tests.

3. Comments: Electrochemical measurement of chloride-induced corrosion of steel was studied, and potential hazards were elucidated; they were then utilised to regulate the findings of the experiments.

8. Challenges and opportunities in corrosion of steel in concrete

Corrosion of steel creates problems from a financial, technical, and pedagogical perspective. There is an increasing need for the correct maintenance and repair of old reinforced concrete structures, and contemporary buildings need to be built to be long-lasting and resistant to wear and tear. This major problem occurs more often in countries with higher levels of affluence. The second problem is the ever-increasing expense of maintaining infrastructure in emerging nations. It's possible that more permanent solutions will still be beneficial to the environment.

8.1 Societal and economic challenges

The study of steel corrosion in concrete has advanced significantly since the middle of the twentieth century, thanks to the work of material scientists, chemists, and civil engineers from various nations. Such an effort was made. In spite of this, it turned out that most of the strategies used didn't work. Corrosion of infrastructures such as gas and oil pipelines, drinking water distribution, electrical utilities, and highway bridges account for half of the direct expenses estimated, while corrosion of ships,

cars, industrial production facilities, and aircraft accounts for the other half [69]. Corrosion's price tag will be plotted against that of other major economic issues, such as obesity, direct costs from nature, climate-related disasters, and annual healthcare costs associated with smoking [70,71]. One may use the figure provided here to better grasp the subject matter. In the next chart, we'll compare the price tag of corrosion to that of a number of other major economic factors, including obesity, direct costs associated with environment and climate change, and climate-related disasters, as well as annual healthcare costs associated with smoking [69].

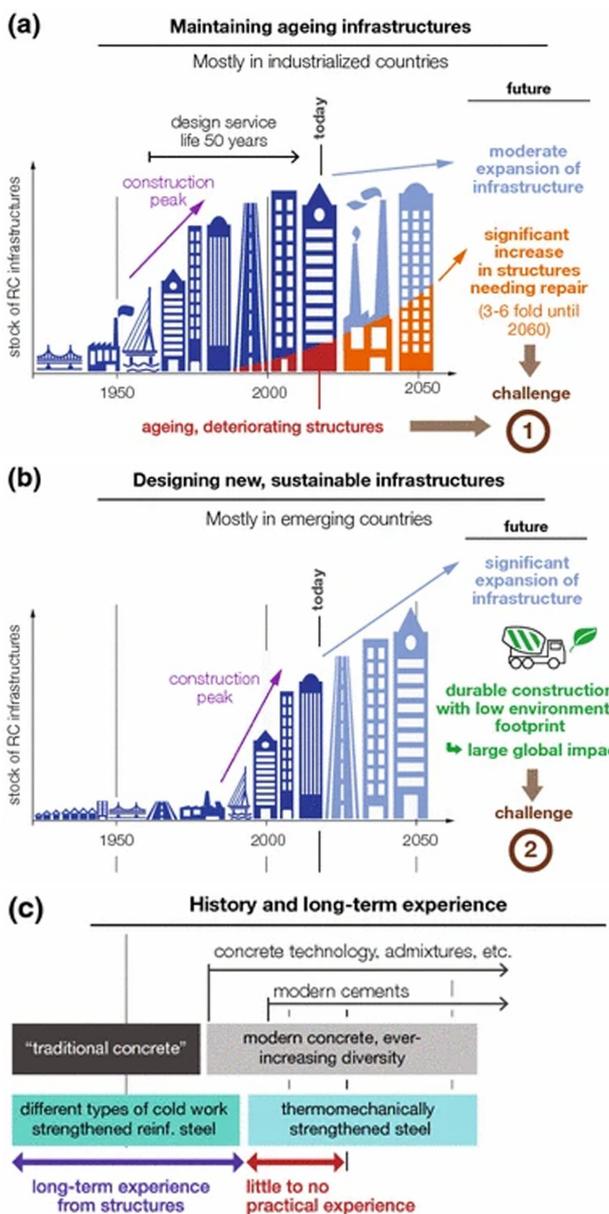


Fig. 6. Technical challenges related to corrosion of steel in different regions [72]

8.2 Technological Challenges

Several technical difficulties are anticipated in this area. The high societal costs of corrosion are a direct reflection of the severe lack of major understanding of corrosion-related degradation of materials exposed to nature, as stated by a committee recently put by the National Research Council of the U.S. to identify challenges in corrosion research and engineering. Scientists are working hard to enhance the technological resources available to prolong the useful life of RC buildings.

This Fig. 6 shows that (a) These are mainly challenged to maintain their stock of existing infrastructures, while emerging countries, (b) Expand their infrastructures are challenging to design durable new structures, (c) It will increase diversity in construction materials and processes and won't permit to rely on long-term empirical service.

Lower pore solution pH, and lower pH buffer capacity will affect a lot in this sector [71].

8.3 Educational Challenges

Problems in the school system will have far-reaching implications on RC structures. If the builders don't have experience in this field, the longevity of the building will be compromised. If they want to perform their jobs well, scientists need to understand how corrosion occurs and why. Steel rebar in concrete may corrode, causing costly repairs if the worker isn't prepared.

9. Recommendations for Future

For the future, here are some suggestions for extending the useful life of RC buildings.

- Scientists and researchers may prioritize remaining service life forecasts for reinforced concrete structures based on the proposed models for carbonation-induced corrosion and chloride-induced corrosion.

- Corrosion data collected from actual structures may be proved to have had a significant role in the development of the model for long-term effects lasting at least a decade. Thus, we shall also include corrosion propagation and subsequent cracking phases.

- In order to extend the useful life of concrete buildings, it is possible to utilise high-strength concrete and various types of steel.

10. Conclusion

This study aimed to fill that knowledge gap by investigating previously unknown influences on steel rebar corrosion in concrete. Corrosion in structural steel is discussed in this research review. It has been found via analysis of various research that steel has a high tendency for corrosion if steel comes into contact with moisture. Concrete contains several chemically active elements, such as oxides of many metals, which contribute to the corrosion of steel studded in concrete and limit its usage. The quantity of chloride in the concrete is a major contributor to rebar corrosion. Concrete's w/c ratio, pH value, porosity, curing, compaction, cement content, etc., all impact corrosion in RC buildings. An in-depth study of these facets will aid in the control of corrosion damage to reinforced concrete structures.

Because of the corrosion problem, RC buildings will have significant setbacks and costs. The root of an issue has to be exposed before it can be fixed properly. A trustworthy technique is required for corrosion monitoring. In the lead-up to any maintenance, demolition, or repair work being done on a reinforced concrete structure, this is very necessary. The corrosion rate is influenced by three variables: exposure to environment (including temperature, humidity, and oxygen availability). This highlights the need to regularly measure the rate of corrosion.

Half-cell potential measurement or Half-cell potential reading is a common method for gauging steel corrosion in concrete. The underlying mechanism of corrosion must also be understood. The potential is seen as a low-

resistance patchwork on the concrete's surface where the steel and concrete meet. Potential readings might be better understood if compared to resistivity readings. Many methods may be effective in measuring the following:

- In order to assess the reinforcement corrosion state, we must identify corroded bars.
- To evaluate the state of a concrete building,
- The purpose of both destructive and non-destructive testing is to make decisions and establish priorities.
- The purpose of managing the corrosion condition of restored RC structures is to identify and evaluate the efficacy of repair efforts.

References

1. R. Hussain and T. Ishida, Multivariable Empirical Analysis of Coupled Oxygen and Moisture for Potential and Rate of Quantitative Corrosion in Concrete, *Journal of Materials in Civil Engineering*, **24**, 7 (2012). Doi: [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0000474](https://doi.org/10.1061/(ASCE)MT.1943-5533.0000474)
2. D. Bjegovic, D. Mikulic, and D. Sekulic, *Proc. 15th World Conference on Non-Destructive Testing*, p. 642, Roma, Italy (2000). <https://www.ndt.net/article/wcndt00/papers/idn642/idn642.htm>
3. S. Ahmad, Reinforcement corrosion in concrete structures, its monitoring and service life prediction—a review, *Cement and Concrete Composites*, **25**, 459 (2003). Doi: [https://doi.org/10.1016/S0958-9465\(02\)00086-0](https://doi.org/10.1016/S0958-9465(02)00086-0)
4. NACE/ASTM G193-12D, Standard Terminology and Acronyms Relating to Corrosion (2012).
5. C. M. Hansson, Comments on electrochemical measurements of the rate of corrosion of steel in concrete, *Cement and Concrete Research*, **14**, 574 (1984). Doi: [https://doi.org/10.1016/0008-8846\(84\)90135-2](https://doi.org/10.1016/0008-8846(84)90135-2)
6. L. J. Parrott, *A review of carbonation in reinforced concrete*, Cement and Concrete Association (1987).
7. A. Zaki, M. A. M. Johari, W. M. A. W. Hussin, and Y. Jusman, Experimental Assessment of Rebar Corrosion in Concrete Slab Using Ground Penetrating Radar (GPR), *International Journal of Corrosion*, **2018**, Article ID 5389829 (2018). Doi: <https://doi.org/10.1155/2018/5389829>
8. M. Alhawat, O. H. Zinkaah, and A. Araba, Study of corrosion products induced under different environmental conditions, *IOP Conference Series: Materials Science and Engineering*, **1090**, 012050 (2021). Doi: <https://doi.org/10.1088/1757-899x/1090/1/012050>
9. P. Schiessl, Report of the Technical Committee 60-CSC-

- RILEM (The International Union of Testing and Research Laboratories for Materials and Structures), Corrosion of Steel in Concrete, London, UK: Chapman and Hall, London (1988).
10. P. Claisse, H. Elsayad, and E. Ganjian, Permeability and Pore Volume of Carbonated concrete European concerted action, *Final report, Brussels* (1997).
 11. T. Visalakshi and S. Bhalla, *Proc. International Conference on Corrosion. CONCOR, New Delhi* (2013).
 12. M. F. Montemor, A. M. P. Simões, and M. G. S. Ferreira, Chloride-induced corrosion on reinforcing steel: from the fundamentals to the monitoring techniques, *Cement and Concrete Composites*, **25**, 491 (2003). Doi: [https://doi.org/10.1016/S0958-9465\(02\)00089-6](https://doi.org/10.1016/S0958-9465(02)00089-6)
 13. M. Moreno, W. Morris, M. G. Alvarez, and G. S. Duffó, Corrosion of reinforcing steel in simulated concrete pore solutions: Effect of carbonation and chloride content, *Corrosion Science*, **46**, 2681 (2004). Doi: <https://doi.org/10.1016/j.corsci.2004.03.013>
 14. H. A. F. Dehwah, M. Maslehuddin, and S. A. Austin, Long-term effect of sulfate ions and associated cation type on chloride-induced reinforcement corrosion in Portland cement concretes, *Cement and Concrete Composites*, **24**, 17 (2002). Doi: [https://doi.org/10.1016/S0958-9465\(01\)00023-3](https://doi.org/10.1016/S0958-9465(01)00023-3)
 15. J. P. Broomfield, *Corrosion of steel in concrete: understanding, investigation and repair, 3rd ed.*, p. 17, Crc Press, Florida (2023).
 16. S. E. Hussain, A. Al-Musallam, and A. S. Al-Gahtani, Factors affecting threshold chloride for reinforcement corrosion in concrete, *Cement and Concrete Research*, **25**, 1543 (1995). Doi: [https://doi.org/10.1016/0008-8846\(95\)00148-6](https://doi.org/10.1016/0008-8846(95)00148-6)
 17. G. K. Glass and N. R. Buenfeld, The presentation of the chloride threshold level for corrosion of steel in concrete, *Corrosion Science*, **39**, 1001 (1997). Doi: [https://doi.org/10.1016/S0010-938X\(97\)00009-7](https://doi.org/10.1016/S0010-938X(97)00009-7)
 18. C. Alonso, C. Andrade, X. R. Nóvoa, M. Izquierdo, and M. C. Pérez, Effect of protective oxide scales in the macrogalvanic behaviour of concrete reinforcements, *Corrosion Science*, **40**, 1379 (1998). Doi: [https://doi.org/10.1016/S0010-938X\(98\)00040-7](https://doi.org/10.1016/S0010-938X(98)00040-7)
 19. T. Maheswaran and J. G. Sanjayan, A semi-closed-form solution for chloride diffusion in concrete with time-varying parameters, *Magazine of Concrete Research*, **56**, 359 (2004). Doi: <https://doi.org/10.1680/mac.2004.56.6.359>
 20. D. Trejo and P. J. Monteiro, Corrosion performance of conventional (ASTM A615) and low-alloy (ASTM A706) reinforcing bars embedded in concrete and exposed to chloride environments, *Cement and Concrete Research*, **35**, 562 (2005). Doi: <https://doi.org/10.1016/j.cemconres.2004.06.004>
 21. T. P. Hoar, The production and breakdown of the passivity of metals, *Corrosion Science*, **7**, 6 (1967). Doi: [https://doi.org/10.1016/S0010-938X\(67\)80023-4](https://doi.org/10.1016/S0010-938X(67)80023-4)
 22. B. Pradhan, Performance of TMT and CTD steel bars, *OPC and blended cements against chloride induced rebar corrosion in concrete*, pp. 116 - 119, Indian Institute of Technology Delhi (2007). <http://eprint.iitd.ac.in/bitstream/handle/2074/6207/TH-3528.pdf?sequence=2&isAllowed=y>
 23. M. Stern and A. L. Geary, Electrochemical polarization: I. A theoretical analysis of the shape of polarization curves, *Journal of the Electrochemical Society*, **104**, 56 (1957). Doi: <https://doi.org/10.1149/1.2428496>
 24. C. Andrade and C. Alonso, Test methods for on-site corrosion rate measurement of steel reinforcement in concrete by means of the polarization resistance method, *Materials and Structures*, **37**, 623 (2004). Doi: <https://doi.org/10.1007/BF02483292>
 25. Ha-Won Song and Velu Saraswathy, Corrosion Monitoring of Reinforced Concrete Structures - A Review, *International Journal of Electrochemical Science*, **2**, 1 (2007). Doi: [https://doi.org/10.1016/S1452-3981\(23\)17049-0](https://doi.org/10.1016/S1452-3981(23)17049-0)
 26. S. Feliu, J. A. González, S. Feliu, and C. Andrade, Relationship between conductivity of concrete and corrosion of reinforcing bars, *British Corrosion Journal*, **24**, 3 (1989). Doi: <https://doi.org/10.1179/000705989798270027>
 27. S. Feliu, J. A. Gonzalez, C. Andrade, and V. Feliu, On-site determination of the polarization resistance in a reinforced concrete beam, *Corrosion*, **44**, 761 (1988). Doi: <https://doi.org/10.5006/1.3584943>
 28. S. Feliu, J. A. González, and M. C. Andrade, Confinement of the electrical signal for in situ measurement of polarization resistance in reinforced concrete, *Materials Journal*, **87**, 457 (1990). Doi: <https://doi.org/10.14359/1830>
 29. S. Feliu, J. A. Gonzalez, and C. Andrade, Errors in the On-site Measurements of Rebar Corrosion Rates Arising From Signal Un Confinement, *Special Publication*, **151**, 183 (1994). Doi: <https://doi.org/10.14359/4383>
 30. J. P. Broomfield, J. Rodriguez, L. M. Ortega, and A. M. Garcia, *Proc. Structural Faults and Repair-93*, pp. 155 – 164, University of Edinburgh, Scotland (1993).
 31. A. Sehgal, Y. T. Kho, K. Osseo-Asare, and H. W. Pick-

- ering, Comparison of corrosion rate-measuring devices for determining corrosion rate of steel-in-concrete systems, *Corrosion*, **48**, 871 (1992). Doi: <https://doi.org/10.5006/1.3315888>
32. S. G. Millard, D. Law, J. H. Bungey, and J. Cairns, Environmental influences on linear polarisation corrosion rate measurement in reinforced concrete, *Ndt & E International*, **34**, 409 (2001). Doi: [https://doi.org/10.1016/S0963-8695\(01\)00008-1](https://doi.org/10.1016/S0963-8695(01)00008-1)
 33. J. A. Gonzalez, S. Feliu, C. Andrade, and I. Rodriguez, On-site detection of corrosion in reinforced concrete structures, *Materials and Structures*, **24**, 346 (1991). Doi: <https://doi.org/10.1007/BF02472067>
 34. V. Feliu, J. A. González, C. Andrade, and S. Feliu, Equivalent circuit for modelling the steel-concrete interface. II. Complications in applying the stern-geary equation to corrosion rate determinations, *Corrosion Science*, **40**, 995 (1998). Doi: [https://doi.org/10.1016/S0010-938X\(98\)00037-7](https://doi.org/10.1016/S0010-938X(98)00037-7)
 35. S. Ahmad and B. Bhattacharjee, A simple arrangement and procedure for in-situ measurement of corrosion rate of rebar embedded in concrete, *Corrosion Science*, **37**, 781 (1995). Doi: [https://doi.org/10.1016/0010-938X\(95\)80008-5](https://doi.org/10.1016/0010-938X(95)80008-5)
 36. G. P. Gu, J. J. Beaudoin, and V. S. Ramachandran, Techniques for corrosion investigation in reinforced concrete Handbook of Analytical Techniques in Concrete Science and Technology, pp. 441-504, William Andrew, New York (2001). Doi: <https://doi.org/10.1016/B978-081551437-4.50015-1>
 37. J. Gao, J. Wu, J. Li, and X. Zhao, Monitoring of corrosion in reinforced concrete structure using Bragg grating sensing, *Ndt & E International*, **44**, 202 (2011). Doi: <https://doi.org/10.1016/j.ndteint.2010.11.011>
 38. S. Park, B. L. Grisso, D. J. Inman, and C.-B. Yun, MFC-based structural health monitoring using a miniaturized impedance measuring chip for corrosion detection, *Research in Nondestructive Evaluation*, **18**, 139 (2007). Doi: <https://doi.org/10.1080/09349840701279937>
 39. J. W. Yang, H. P. Zhu, J. Yu, and D. S. Wang, Experimental study on monitoring steel beam local corrosion based on EMI technique, *Applied mechanics and materials*, **273**, 623 (2013). Doi: <https://doi.org/10.4028/www.scientific.net/AMM.273.623>
 40. N. J. Carino, Nondestructive techniques to investigate corrosion status in concrete structures, *Journal of Performance of Constructed Facilities*, **13**, 96 (1999). Doi: [http://dx.doi.org/10.1061/\(ASCE\)0887-3828\(1999\)13:3\(96\)](http://dx.doi.org/10.1061/(ASCE)0887-3828(1999)13:3(96))
 41. S. K. Verma, S. S. Bhadauria, and S. Akhtar, Monitoring corrosion of steel bars in reinforced concrete structures, *The Scientific World Journal*, **2014**, Article ID 957904 (2014). Doi: <https://doi.org/10.1155/2014/957904>
 42. M. Pour-Ghaz, O. B. Isgor, and P. Ghods, Quantitative interpretation of half-cell potential measurements in concrete structures, *Journal of Materials in Civil Engineering*, **21**, 467 (2009). Doi: [https://doi.org/10.1061/\(ASCE\)0899-1561\(2009\)21:9\(467\)](https://doi.org/10.1061/(ASCE)0899-1561(2009)21:9(467))
 43. A. Elshami and B. National, Efficiency of Corrosion Inhibitors Used For Concrete Structures in Aggressive Environment (2021).
 44. J. Park and M. Jung, Evaluation of the corrosion behavior of reinforced concrete with an inhibitor by electrochemical impedance spectroscopy, *Materials*, **14**, 5508 (2021). Doi: <https://doi.org/10.3390/ma14195508>
 45. Y. Almashakbeh, E. Saleh, and N. M. Al-Akhras, Evaluation of Half-Cell Potential Measurements for Reinforced Concrete Corrosion, *Coatings*, **12**, 975 (2022). Doi: <https://doi.org/10.3390/coatings12070975>
 46. H. Xu, Z. Chen, B. Xu, and D. Ma, Impact of Low Calcium Fly Ash on Steel Corrosion Rate and Concrete-Steel Interface, *The Open Civil Engineering Journal*, **6**, 1 (2012). Doi: <https://doi.org/10.2174/1874149501206010001>
 47. M. Maslehuddin, Rasheeduzzafar, and A. I. Al-Mana, Strength and corrosion resistance of superplasticized concretes, *Journal of Materials in Civil Engineering*, **4**, 108 (1992). Doi: [https://doi.org/10.1061/\(ASCE\)0899-1561\(1992\)4:1\(108\)](https://doi.org/10.1061/(ASCE)0899-1561(1992)4:1(108))
 48. M. Criado, D. M. Bastidas, S. Fajardo, A. Fernández-Jiménez, and J. M. Bastidas, Corrosion behaviour of a new low-nickel stainless steel embedded in activated fly ash mortars, *Cement and Concrete Composites*, **33**, 644 (2011). Doi: <https://doi.org/10.1016/j.cemconcomp.2011.03.014>
 49. H. E. Jamil, A. Shriiri, R. Boulif, M. F. Montemor, and M. G. S. Ferreira, Corrosion behaviour of reinforcing steel exposed to an amino alcohol based corrosion inhibitor, *Cement and Concrete Composites*, **27**, 671 (2005). Doi: <https://doi.org/10.1016/j.cemconcomp.2004.09.019>
 50. K. K. Sideris and A. E. Savva, Durability of mixtures containing calcium nitrite based corrosion inhibitor, *Cement and Concrete Composites*, **27**, 277 (2005). Doi: <https://doi.org/10.1016/j.cemconcomp.2004.02.016>
 51. K.-Y. Ann, H. S. Jung, H. S. Kim, S. S. Kim, and H. Y. Moon, Effect of calcium nitrite-based corrosion inhibitor in preventing corrosion of embedded steel in concrete, *Cement and Concrete Research*, **36**, 530 (2006). Doi: <https://doi.org/10.1016/j.cemconcomp.2004.02.016>

- <https://doi.org/10.1016/j.cemconres.2005.09.003>
52. A. A. Gürten, M. Erbil, and K. Kayakırlmaz, Effect of polyvinylpyrrolidone on the corrosion resistance of steel, *Cement and Concrete Composites*, **27**, 802 (2005). Doi: <https://doi.org/10.1016/j.cemconcomp.2005.03.002>
 53. W. Morris and M. Vazquez, A migrating corrosion inhibitor evaluated in concrete containing various contents of admixed chlorides, *Cement and Concrete Research*, **32**, 259 (2002). Doi: [https://doi.org/10.1016/S0008-8846\(01\)00669-X](https://doi.org/10.1016/S0008-8846(01)00669-X)
 54. S. U. Al-Dulaijan, M. Maslehuddin, M. Shameem, M. Ibrahim, and M. Al-Mehthel, Corrosion protection provided by chemical inhibitors to damaged FBEC bars, *Construction and Building Materials*, **29**, 487 (2012). Doi: <https://doi.org/10.1016/j.conbuildmat.2011.10.009>
 55. C. Monticelli, A. Frignani, and G. Trabaneli, A study on corrosion inhibitors for concrete application, *Cement and Concrete Research*, **30**, 635 (2000). Doi: [https://doi.org/10.1016/S0008-8846\(00\)00221-0](https://doi.org/10.1016/S0008-8846(00)00221-0)
 56. O. T. de Rincon, O. Perez, E. Paredes, Y. Caldera, C. Urdaneta, and I. Sandoval, Long-term performance of ZnO as a rebar corrosion inhibitor, *Cement and Concrete Composites*, **24**, 79 (2002). Doi: [https://doi.org/10.1016/S0958-9465\(01\)00029-4](https://doi.org/10.1016/S0958-9465(01)00029-4)
 57. V. Nachiappan and E. H. Cho, Corrosion of high chromium and conventional steels embedded in concrete, *Journal of Performance of Constructed Facilities*, **19**, 56 (2005). Doi: [https://doi.org/10.1061/\(ASCE\)0887-3828\(2005\)19:1\(56\)](https://doi.org/10.1061/(ASCE)0887-3828(2005)19:1(56))
 58. M. Badawi and K. Soudki, Control of corrosion-induced damage in reinforced concrete beams using carbon fiber-reinforced polymer laminates, *Journal of Composites for Construction*, **9**, 195 (2005). Doi: [https://doi.org/10.1061/\(ASCE\)1090-0268\(2005\)9:2\(195\)](https://doi.org/10.1061/(ASCE)1090-0268(2005)9:2(195))
 59. S. A. Civjan, J. M. LaFave, J. Trybulski, D. Lovett, J. Lima, and D. W. Pfeifer, Effectiveness of corrosion inhibiting admixture combinations in structural concrete, *Cement and Concrete Composites*, **27**, 688 (2005). Doi: <https://doi.org/10.1016/j.cemconcomp.2004.07.007>
 60. F. Wombacher, U. Maeder, and B. Marazzani, Aminoalcohol based mixed corrosion inhibitors, *Cement and Concrete Composites*, **26**, 209 (2004). Doi: [https://doi.org/10.1016/S0958-9465\(03\)00040-4](https://doi.org/10.1016/S0958-9465(03)00040-4)
 61. H.-S. So and S. G. Millard, Assessment of corrosion rate of reinforcing steel in concrete using Galvanostatic pulse transient technique, *International Journal of Concrete Structures and Materials*, **1**, 83 (2007). Doi: <https://doi.org/10.4334/IJCSM.2007.1.1.083>
 62. J. Cairns and C. Melville, The effect of concrete surface treatments on electrical measurements of corrosion activity, *Construction and Building Materials*, **17**, 301 (2003). Doi: [https://doi.org/10.1016/S0950-0618\(03\)00028-X](https://doi.org/10.1016/S0950-0618(03)00028-X)
 63. R. R. Hussain, Underwater half-cell corrosion potential bench mark measurements of corroding steel in concrete influenced by a variety of material science and environmental engineering variables, *Measurement*, **44**, 274 (2011). Doi: <https://doi.org/10.1016/j.measurement.2010.10.002>
 64. M. H. Faber and J. D. Sorensen, Indicators for inspection and maintenance planning of concrete structures, *Structural Safety*, **24**, 377 (2002). Doi: [https://doi.org/10.1016/S0167-4730\(02\)00033-4](https://doi.org/10.1016/S0167-4730(02)00033-4)
 65. W.-L. Lai, T. Kind, M. Stoppel, and H. Wiggenshauser, Measurement of accelerated steel corrosion in concrete using ground-penetrating radar and a modified half-cell potential method, *Journal of Infrastructure Systems*, **19**, 205 (2013). Doi: [https://doi.org/10.1061/\(ASCE\)IS.1943-555X.0000083](https://doi.org/10.1061/(ASCE)IS.1943-555X.0000083)
 66. B. Elsener, Macrocell corrosion of steel in concrete—implications for corrosion monitoring, *Cement and Concrete Composites*, **24**, 65 (2002). Doi: [https://doi.org/10.1016/S0958-9465\(01\)00027-0](https://doi.org/10.1016/S0958-9465(01)00027-0)
 67. H. R. Soleymani and M. E. Ismail, Comparing corrosion measurement methods to assess the corrosion activity of laboratory OPC and HPC concrete specimens, *Cement and Concrete Research*, **34**, 2037 (2004). Doi: <https://doi.org/10.1016/j.cemconres.2004.03.008>
 68. A. Poursaee and C. M. Hansson, Potential pitfalls in assessing chloride-induced corrosion of steel in concrete, *Cement and Concrete Research*, **39**, 391 (2009). Doi: <https://doi.org/10.1016/j.cemconres.2009.01.015>
 69. X. Xu, E. E. Bishop, S. M. Kennedy, S. A. Simpson, and T. F. Pechacek, Annual healthcare spending attributable to cigarette smoking: an update, *American Journal of Preventive Medicine*, **48**, 326 (2015). Doi: <https://doi.org/10.1016/j.amepre.2014.10.012>
 70. M. M. H. Tusher, Microbial Synthesis of Cadmium Selenide Quantum Dots (CdSe QDs), Influencing Factors and Applications, *Optical and Quantum Electronics*, **55**, 332 (2023). Doi: <https://doi.org/10.1007/s11082-023-04632-z>
 71. A. B. Smith and R. W. Katz, US billion-dollar weather and climate disasters: data sources, trends, accuracy and biases, *Natural Hazards*, **67**, 387 (2013). Doi: <https://doi.org/10.1007/s11069-013-0566-5>
 72. U. M. Angst, Challenges and opportunities in corrosion of steel in concrete, *Materials and Structures*, **51**, Article number 4 (2018). Doi: <https://doi.org/10.1617/s11527-017-1131-6>